

6-1-2019

Section: Chemistry

IMPACT OF NANOSIZED SILICA ON THE PHYSICO-MECHANICAL PROPERTIES AND CORROSION PROTECTION OF CONCRETE

Elsayed Elnaggar

Department of Chemistry, Faculty of Science - Al - Azhar University, Cairo, Egypt,
elsayed_elmhdy80@yahoo.com

Tarek Elsokkary

Housing and Building National Research Center, Raw Building Materials Technology and Processing Research Institute, Cairo, Egypt, tarek_elsokkary@yahoo.com

Mostafa Shohide

Housing and Building National Research Center, Raw Building Materials Technology and Processing Research Institute, Cairo, Egypt., maxem505016@yahoo.com

Basil El - Sabbagh

Housing and Building National Research Center, Raw Building Materials Technology and Processing Research Institute, Cairo, Egypt

Follow this and additional works at: <https://absb.researchcommons.org/journal>

 Part of the [Life Sciences Commons](#)

How to Cite This Article

Elnaggar, Elsayed; Elsokkary, Tarek; Shohide, Mostafa; and El - Sabbagh, Basil (2019) "IMPACT OF NANOSIZED SILICA ON THE PHYSICO-MECHANICAL PROPERTIES AND CORROSION PROTECTION OF CONCRETE," *Al-Azhar Bulletin of Science*: Vol. 30: Iss. 1, Article 18.

DOI: <https://doi.org/10.21608/absb.2019.67893>

This Original Article is brought to you for free and open access by Al-Azhar Bulletin of Science. It has been accepted for inclusion in Al-Azhar Bulletin of Science by an authorized editor of Al-Azhar Bulletin of Science. For more information, please contact kh_Mekheimer@azhar.edu.eg.

IMPACT OF NANOSIZED SILICA ON THE PHYSICO-MECHANICAL PROPERTIES AND CORROSION PROTECTION OF CONCRETE

Elsayed M. Elnaggar^a, Tarek M. Elsokkary^b, Mostafa A. Shohide^{b*} and Basil A El-Sabbagh^b

^a *Department of Chemistry, Faculty of Science- Al-Azhar University, Cairo, Egypt.*

^b *Housing and Building National Research Center, Raw Building Materials Technology and Processing Research Institute, Cairo, Egypt.*

*Corresponding author: maxem505016@yahoo.com

ABSTRACT

Nanomaterials have an important role for enhancing the concrete properties and inhibition of rebar corrosion in reinforced concrete. Nanosilica (NS) is one of the most effective cementitious materials, which possess high pozzolanic nature. In this work, NS was added in mix design of concrete with different ratios as; 0, 0.5, 1, 1.5, 2 and 2.5 % by weight of Portland cement. Physical, mechanical properties (workability, density) were determined for the fresh concrete samples. While, compressive strength and microstructural properties of the interfacial transition zone (ITZ) between cement pastes and aggregates of concrete were investigated for the hardened samples. As well as electrochemical measurements (open circuit potential and linear polarization) were done for the reinforced concrete samples. The results show that, concretes containing NS up to 2% have a higher compressive strength and a denser interfacial transition zone (ITZ). Also, corrosion inhibition for reinforced concrete increased gradually by increasing NS addition up to 2%.

Keywords: Concrete, nanosilica, corrosion of reinforced concrete

1. INTRODUCTION

Nanotechnology (NT) is defined as the science of studying, examining and monitoring the behavior and performance of materials at the nano-scale. It is the process of production a material or device with building units at the atomic and molecular scale [1,2]. Nanotechnology covers a wide scope and many disciplines stimulating collaboration among scientists and researchers in sustainable development [3, 4]. These developments have begun to emerge in civil engineering by using NT to improve the properties of cement and concrete [5]. Lotfi et al. studied the properties of cement mortar containing both of nanosilica (NS) and silica fume (SF). They found that the compressive strength values for mortar containing NS particles were higher than that of mortar containing SF at 7 to 28 days [6]. Abd El-Aleem et al. studied hydration characteristics, thermal expansion and microstructure of cement containing NS. They have been reported that, partially substitution of OPC up to 5 mass % NS improves the mechanical and microstructural characteristics in comparison with the neat OPC paste up to 90 days [7]. Prasa da Raet al. studied the

influence of fly ash (FA) and nanosilica (NS) on strength properties of concrete. Cement is partially replaced by 20 and 30 % of FA and NS 1.5, 3 and 4.5 % by weight. It can be concluded that, with the increase in NS percentage, various strength characteristics of concrete increase up to 3%, with further increase in NS the strength characteristics of concrete are decreased for the given percentages of FA possesses improved properties compared to the controlled concrete [8]. El-Didamony et al. studied the hydration behavior of composite cement containing FA and NS [9]. Tawfik et al. have investigated the influence of nano-particles on mechanical and nondestructive properties of high-performance concrete. The results showed that, both of FA and NS improve the hydration behavior and mechanical properties of the investigated cements. But, NS possesses higher improvement level than FA [10]. Ozyildirim et al. investigated how nano-material improved permeability and strength of concrete and found that, very little amount of NMs like nano silica and nano clay in concrete can improve the compressive strength and permeability of concrete [11]. Mohammed investigated the influence of using different

cement blends on the concrete properties incorporating nano materials. There was a significant positive effect of using ternary blends on the different mechanical properties [12]. Isfahani *et al.* investigated the effect of replacement different proportions of cement by nano-silica on the compressive strength and durability of hardened concrete with different w/b ratios [13]. [Montgomery](#) *et al.* studied the effect of replacement different ratios as; 1, 3 and 5 % cement with silica nano-particles by volume on the compressive strength. The study revealed that, 1% is the optimum cement replacement percentage to increase the compressive strength [14]. Younis and Mustafa improved the performance of recycled aggregate concrete by using nanosilica. The study results show that silica nano-particles can improve the compressive and tensile strength values, reduce the permeability, and also modify the microstructure of recycled aggregate concrete [15]. Several studies have shown that, the addition of NS results in improved compressive, tensile, and flexural strength of concrete [16-18]. Also, the addition of NS in concrete mix design contributes to improve the microstructure of the obtained hardened concrete [19, 20]. Furthermore, there are many researches proved that NS have an important mechanism for inhibition the corrosion of steel rebar in reinforced concrete [21, 22, 23]. The aim of this work was to study the effect of NS addition to concrete mix with different ratios of the cement weight on the physico-mechanical properties and corrosion protection of concrete.

2. MATERIALS AND METHODS

2.1. Materials

Cementitious materials in this study are Portland cement and silica nano-particles. Ordinary Portland cement (type CEM I - 42.5 N) is produced from El- Suez Company (El Suez plant) in Egypt. Silica nano-particles are exported from India. Chemical properties of cement and silica nano-particles are pointed in Table 1. The super-plasticizer (SP) is naphthalene type with 33% solid content and 1.15 g/cm³ density. The used coarse aggregate is a natural crushed stone of dolomite. It is generated from the quarries and crushers located at Attaqa Mountains (Cairo-Suez

Desert Rd.). Steel rebar obtained from Ezz steel Company, Alexandria, Egypt. Its radius is 12mm.

2.2. Methods

2.2.1. Characteristics of raw materials

2.2.1.1. Characteristics of Portland cement

A. Chemical characteristics of Portland cement

Chemical Characteristics of Portland cement (PC) used were carried out to determine the type and percentage of the major oxides present in it using the following techniques and methods: The major oxides of the investigated cement was determined by X-ray fluorescence (XRF). The test was run using Rh- α (rubidium) radiation tube at 50 Kv and 50 mA. In the present work, quantitative determination of the major oxides; SiO₂, Al₂O₃, Fe₂O₃, TiO₂, CaO, MgO, Na₂O, K₂O and SO₃ were accomplished by a computerized X-ray fluorescence (Phillips PW 1400 Spectrometer, Holland). Also, a traditional manual method prescribed in ASTM D7348-08 for determination of loss on ignition (LOI) was followed.

B. Physical and mechanical characteristics of Portland cement

The supplied OPC sample was studied in terms of determination the expansion of cement by the LE CHATELIER method (ESS 2421-1993), determination of initial and final setting times of cement paste using Vicat's apparatus (ASTM C191-08) and compressive strength (E.S 2421 part 7 – 2005).

2.2.1.2. Characterization of fine and coarse aggregates

All the physical and chemical properties of fine and coarse aggregates determined according to the Egyptian code for design and construction structures (ECP 203-2001 (2007)).

2.2.1.3. Chemical analysis of mixing water (drinking water)

The chemical composition of the drinking water which is used as mixing water in the concrete specimens preparation are determined according to ECP 203-2001.

2.2.1.4. Characteristics of nanosilica

A. Chemical analysis of nanosilica by (XRF)

The chemical analysis of used nanosilica was determined by X-ray fluorescence (XRF).

B. X-Ray Diffraction (XRD)

The XRD technique was used to determine the mineralogical composition of the investigated material. The used XRD apparatus was X'Pert PRO PW 3040/60 (PANalytical) diffractometer equipped with monochromatic Cu- α radiation source. The test was run at 40 Kv and 30 mA. A continuous mode was used for collecting data in the 2θ range from 5° - 50° at a scanning speed of 2° /min. The acquired data were analyzed using X'pert High Score software including cards of International Center of Diffraction Data.

C. Transmission electron microscopy (TEM)

TEM is one of the useful and widely used tools to determine size and morphology of nano particles. Transmission electron microscopy (TEM) allows a qualitative understanding of the internal structure. TEM specimens were prepared by ultra-sonic materials for 15 minutes before analysis. The test was performed by a JEOL JEM-1230; model Oregon (Japan) at 80 kV.

2.2.1.5. Chemical analysis of steel rebar

The chemical constituents of rebar used in this study are determined by the chemical analysis of rebar according to ASTM E 415-08.

2.2.2. Preparation of concrete samples

For each mix proportion, concrete cubes measuring $100 \times 100 \times 100$ mm³ for compressive strength test and 150 mm cylinders for water absorption and electrochemical measurements were prepared. In order, SP and water were mixed together in mixer, and then NS particles

were added, and mixed for 5 minutes with high speed. Then cement, fine and coarse aggregates were added for three minutes in rotary mixer with low speed to procure a fresh workable mixture of concrete. Finally, fresh concrete were casted in steel molds in three layers and vibrated by using a shaker for consolidation purpose and reduce existing air voids in the matrix of fresh concrete. Specimens were demolded after 24 h and cured in the curing room. Mix proportions of concrete samples listed in Table 1.

2.2.3. Evaluation of concrete samples

2.2.3.1. Workability and density of fresh concrete samples

Slump and density (unit weight) tests were determined according to ASTM C143-03 (2003) and ASTM C138 respectively. Density expressed by the following:

$$D = (M_c - M_m) / V_m.$$

M_c is weight of the measure holding the concrete; M_m is weight of the empty concrete measure and V_m is the volume of the measure.

2.2.3.2. Compressive strength of hardened concrete samples

Compressive strength test for hardened concrete samples was carried out by using a 2000 KN compression machine according to ASTM C109 (2011). The hardened cubes were tested at a saturated surface dry condition to avoid of water that fills the pores of the specimens. Compressive strength value of any mix of concrete sample represented as the mean of three readings of compressive strength for three cubes of the same concrete mix.

2.2.3.3. Scanning electron micrograph of concrete samples

Table 1. Mix proportions (kg/m³ of concrete)

Mix	Cement g/m ³	Dolomite g/m ³	Sand g/m ³	Water g/m ³	Nano Silica g/m ³	S.P.* g/m ³
C	400	1124.8	750.0	160.0	0	6.00
M1	400	1120.6	747.0	160.8	2	6.03
M2	400	1116.4	744.3	161.6	4	6.06
M3	400	1112.2	741.5	162.4	6	6.09
M4	400	1108.0	738.6	163.2	8	6.12
M5	400	1104.0	736.0	164.0	10	6.15

* Super Plasticizer

After determining mechanical properties, the selective crushed specimens were tested by SEM to observe the effect of nanosilica addition on properties of Interfacial Transition Zone (ITZ) between cement paste and aggregates. The scanning electron micrographs were taken using an Inspect S machine (FEI Company, Holland). The microscope can examine the microstructure of the fractured composites at accelerating voltage of 200 V to 30 KV and power zoom magnification up to 300000 xs.

2.3.3.4. Corrosion resistance measurements

Concrete cylinders were immersed in 3.5% NaCl as aggressive medium for 28 days, then corrosion parameters measured by Potentiostat instrument as shown in Fig. 1.



Fig. 1. Potentiostat

A. Open circuit potential (OCP)

In this work, this technique is used for measuring the scope of steel rebar susceptibility to react with an environment. Where concrete represented as an electrolyte and reinforcement will enhance a potential dependent on the concrete environment. For reinforcement concrete structures, OCP technique is depending on measurement the corrosion potential of steel rebar (working electrode) with respect to a standard reference

electrode such as standard calomel electrode (SCE).

B. Linear polarization (polarization resistance) technique

This technique determines the effect of N_s addition content on the corrosion of steel rebar through measuring the corrosion rate.

3. RESULTS AND DISCUSSIONS

3.1. Characteristics of raw materials

3.1.1. Characteristics of Portland cement

3.1.1.1. Chemical composition of Portland cement

Table 2. Chemical composition of Ordinary Portland cement (OPC)

Oxide	Result (%)	ESS 4576-1/2013
SiO ₂	20.79	
Al ₂ O ₃	4.01	
Fe ₂ O ₃	3.08	
CaO	62.17	
MgO	2.69	
SO ₃	2.69	<3.50
L.O.I	3.94	<5.00
Na ₂ O	0.18	
K ₂ O	0.07	
Total	99.91	
Insoluble residue	1.21	<5.00
Cl ⁻	0.05	≤0.10 %
Na ₂ O Eq.	0.22	≤0.6 %
LSF	0.92	
C ₃ A	5.42	

3.1.1.2. Physical and mechanical properties of the used Portland cement

The physical and mechanical properties of Ordinary Portland Cement used in this study are illustrated in Table 3. It is noticed that the

Table 3. Results of the physical and mechanical properties of the used OPC.

Item	Test	Test value	ESS limits
Physical properties	Le Chatelier expansion	1.2 mm	<10 mm
	Initial setting time	150 min.	>45 min.
	Final setting time	190 minutes	---
Mechanical properties	Compressive strength (N/mm ²)		
	2 Days	20.00	>10
	7 Days	23.00	>16
	28 Days	50.00	42.5 X ≤ 62.50

results of all physical and mechanical properties for used OPC are achieve the ESS 4756-2005.

3.1.2. Characteristics of coarse and fine aggregates

3.1.2.1. Chemical and physical characteristics of fine aggregate

The studied physical and chemical properties fulfill the requirements of the ECP 203-2001 (2007) as shown in Table 4.

3.1.2.2. Chemical and physical characteristics of coarse aggregate

Table 5 show the chemical and physical characteristics results of coarse aggregate used in this study. The chemical and physical characteristics results of coarse aggregate comply with ESS.

3.1.3. Chemical properties of mixing water (drinking water)

The chemical composition of the drinking

water, which is used as mixing water in the concrete specimen's preparation shows that, it is clear and free from salts and conformable for using in such purpose. Excessive impurities in mixing water not only may affect setting times and concrete strength, but also may cause efflorescence, staining, corrosion of reinforcement, volume instability, and reduced durability. All the studied parameters match the limits of ECP 203-2001. The test results are mentioned in Table 6.

3.1.4. Characteristics of nanosilica

3.1.4.1. Chemical analysis of nano silica by XRF

Table 7. shows XRF results of NS. It is found that the SiO₂ content represents 94. 50 %.

B. X-Ray Diffraction(XRD)

Table 4. Chemical and physical characteristics of fine aggregate

Item	Test	Test value	ESS limits
Physical properties	Specific gravity	2.65	N.D*
	Bulk density (ton/m ³)	1.65	N.D*
	Clay and other fine materials by volume (%)	2.09	<3.00
Chemical properties	Chlorides (%)	0.023	<0.06
	Sulfate (%)	0.028	<0.40
	Organic impurities	Non	No organic impurities in sample

Table 5. Chemical and physical characteristics of coarse aggregate

Item	Test	Value	ESS limits
Physical properties	Specific gravity	2.75	2.50-2.75
	Bulk density (ton/m ³)	1.63	N.D
	Clay and other fine materials by weight (%)	0.22	<3.00
	Water absorption (%)	2.47	2.50
Chemical properties	Chlorides (%)	0.022	<0.04
	Sulfates (%)	0.012	<0.40

Table 6. Results of the chemical properties of the used mixing water

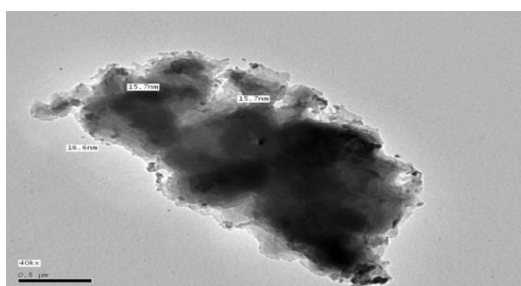
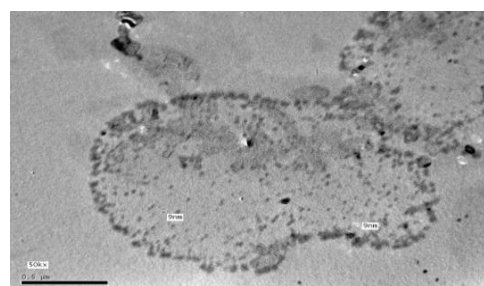
Item	Test	Test value	ESS limits mg/L
Chemical properties	Chlorides as Cl ⁻ (ppm)	36.00	<500.00
	Sulfates as SO ₃ (ppm)	75.00	<300.00
	Total soluble salts (ppm)	387.00	<2000.00

Table 7.XRF results of nanosilica

Item	Na ₂ O	MgO	Al ₂ O ₃	SiO ₂	SO ₃	Cl	CaO	Fe ₂ O ₃	LOI
Value %	0.87	0.18	0.33	94. 50	0.16	0.69	0.33	0.08	3.37

Fig. 2. XRD pattern of nanosilica

From Fig.2, by applying X-Ray Diffraction test (XRD), it was found that the used nanosilica was in amorphous phase. Where, Fig. 2 showed strong broad peaks between 20° and 30° (2θ). These peaks indicated characteristic of amorphous SiO_2 , which has

**(a)****(b)****Fig. 3. TEM of nanosilica**

C. Transmission electron microscopy (TEM)

Fig. 3 shows TEM image of nanosilica sample. The TEM image shows the grain size of the nanosilica ranging between 9-16 nm.

3.1.5. Chemical constituents of steel rebar

Table 8 shows the Chemical constituent results of the used rebar. It is found that the Fe constituent is 98.20.

3.2. Evaluation of concrete samples

3.2.1. Workability and Density of the prepared concrete samples

Slump and density values for each mix proportion are listed in table (8). These values

Table 8. Chemical constituents of steel rebar used

Constituents	Wt (%)	Limits	Constituents	Wt (%)	Limits	Constituents	Wt (%)	Limit
C	0.247	--	Cu	0.317	--	Zn	<0.0020	--
Si	0.202	--	Co	0.014	--	As	0.015	--
Mn	0.75	--	Ti	<0.0010	--	Bi	<0.0020	--
P	0.019	Not more than 0.060	Nb	<0.0030	--	Ca	0.0005	--
S	0.043	Not more than 0.060	V	0.0062	--	Ce	<0.0030	--
Cr	0.078	--	W	<0.010	--	Zr	0.0040	--
Ni	0.063	--	Pb	<0.0030	--	La	<0.0010	--
Mo	0.016	--	B	0.0010	--	Fe	98.20	--
Al	<0.0010	--	Sn	0.018	--	-		--

suitable specific surface regarding its dissimilar structure, and is used as concrete admixture.

recorded for fresh concrete specimens.

Table 9. Workability and density of prepared concrete samples

Mix	Slump, mm	Density (unit weight), g/cm ³
C	100	2.53
M1	80	2.48
M2	65	2.47
M3	50	2.45
M4	45	2.42
M5	40	2.38

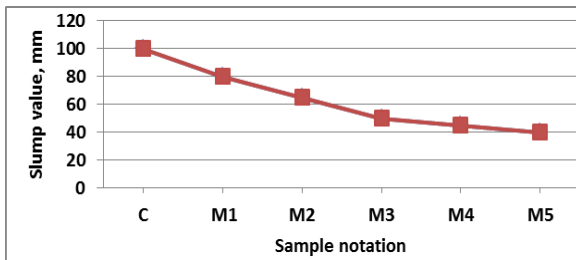


Fig. 4. Slump test results of concrete samples

Table 9 shows slump test results of fresh concrete mixtures for each mix proportion. It is noticed that; the slump values decreased by increasing NS content in the concrete mixture as shown in Fig.4. This is due to extremely high specific surface area of silica nanoparticles, which is accompanied by absorption of large part of water in the concrete mixture [24]. Accordingly, by increasing the nanosilica content in the concrete mixture, resulting in more absorption of water and consequently more loss in the slump [25, 26].

3.2.2. Compressive strength of cured concrete samples

Table 10. Compressive strength of cured concrete samples

Mix	Average of compressive strength, Mpa		
	3 days	7 days	28 days
C	20.0	30.3	52.2
M1	18.7	27.6	55.0
M2	19.0	26.3	57.3
M3	17.9	25.8	59.8
M4	18.8	30.6	64.2
M5	16.7	28.7	60.3

The compressive strength of the cured concrete specimens was tested for different time periods of curing as 3, 7 and 28 days. After curing periods, concrete cubes were crushed at the specified time to determine the strength values. The average compressive values are shown in Table 10.

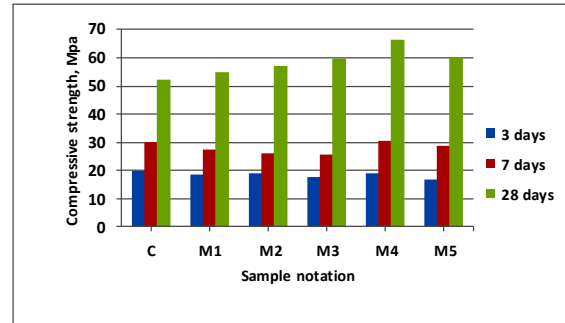



Fig. 5. Compressive strength of cured concrete samples

Table 9 shows the compressive strength results for concrete specimens at different ages of curing. It is noticed that, nanosilica improved compressive strength of concrete, and M4 specimen recorded the maximum strength value at 28 days. Also Fig5 show compressive strength increases with increasing of nanosilica content up to 2%. This can be attributed to the following mechanism:

Due to the reaction of water and cement in the concrete mixture, large amounts of calcium hydroxide Ca(OH)₂ are formed in the interfacial transition zone (ITZ) between aggregates and cement pastes matrix. These crystals of Ca(OH)₂ negatively affected on the strength of concrete as observed in the following equations:



A chemical reaction occurred between silica nano particles and Ca(OH)₂ producing calcium silicate hydrate (C-S-H) condensed gel. This reaction known as pozzolanic reaction and expressed by the following equation:



As a result of this pozzolanic reaction, the amounts of Ca(OH)₂ are consumed in the production of C-S-H gel that is filling the empty spaces in the interfacial transition zone (ITZ) resulting in enhancement strength and consequently durability of concrete improved [27, 28]. Moreover, the strength enhancement

of the prepared concretes may be attributed to the reduced porosity and improvement microstructure of the concrete due to the addition of the nano-particles of SiO_2 [15]. In several researches, it was observed that, the compressive strength increased as a result using of nanosilica but at different dosage [29-32]. Also, it is noticed that, increasing the addition of nanosilica more than 2% in mix proportion of concrete, the compressive strength not increased. This is because of the agglomeration that occurred during the process of mixing and consequently cannot fill the pores in the concrete [28, 33].

3.3.3. Scanning electron microscope (SEM)

The SEM micrographs (at magnification 5000) for the specimens are shown below from Fig 6 to Fig.11.

Figs. 6 to 11 indicate the results of the SEM test. These figures show the results of the examination of concrete matrix microstructure

from samples C, M1, M2, M3, M4 and M5. It can be noticed that, as the nanosilica amount in mix design increases, the concrete matrix becomes denser in the interfacial transition zone, which can be a result of a severe pozzolanic characteristic of silica nanostructures and formation of the dense gel of Calcium-Silicate -Hydrate on one side, and high micro-filling characteristic of these particles on the other side.

3.3.5. Corrosion

The sample M4 was low performance, so it was excluded in corrosion inhibition tests.

3.3.5.1. Open circuit potential (OCP)

The addition of NS affects the corrosion behavior of steel rebar that impeded in concrete samples of C, M1, M2, M3 and M4 that immersed in 0.5 M NaCl solution for 28 days was investigated by potential-time (OCP) curve measurement for 30 minutes as shown in Fig 12.

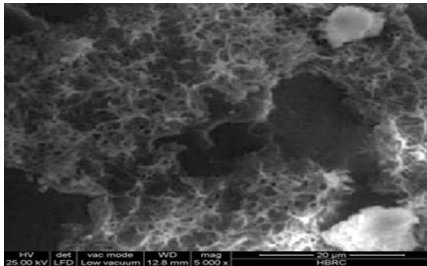


Fig. 6. SEM of C

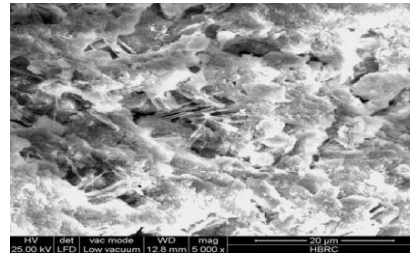


Fig. 7. SEM of M1

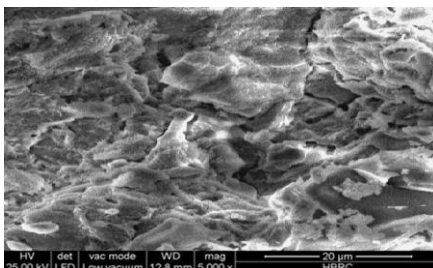


Fig. 8. SEM of M2

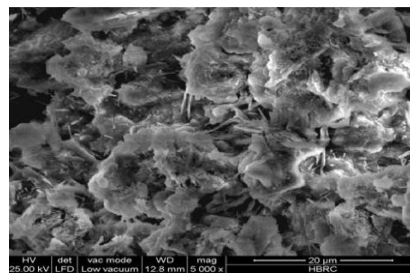


Fig. 9. SEM of M3

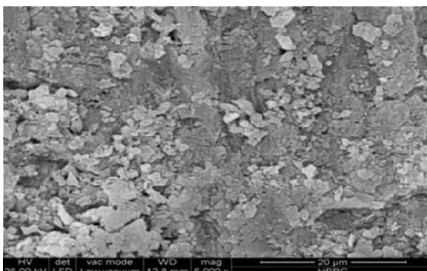


Fig. 10. SEM of M4 sample

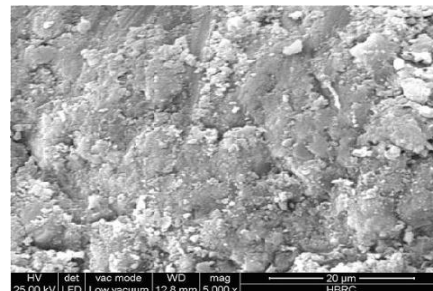


Fig. 11. SEM of M5

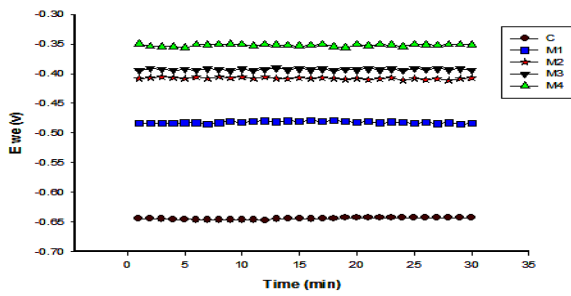


Fig. 12. OCP curves of reinforcement concrete samples

Fig.12 shows that, C specimen have the lowest E-ocp final reading value. This mean that steel rebar impeded in C concrete specimen have the highest tendency to corrosion, and the E-ocp values for M1, M2, M3 and M4 specimens shifted gradually toward the anode side of C to: (-484 mv), (-407 mv), (-393 mv) and (-351 mv) respectively. This regular shifting to positive region, means that the tendency to corrosion decreased by increasing the addition content of nanosilica up to 2%. This because of NS addition, which caused in enhanced concrete durability and consequently the improvement rebar protection from corrosion.

3.3.5.2. Linear polarization (polarization resistance)

The polarization curves for reinforcement concrete samples of C, M1, M2, M3 and M4 immersed in 0.5 M NaCl solution were illustrated in Fig. 13. Examination of this figure shows that current decreased gradually with NS addition.

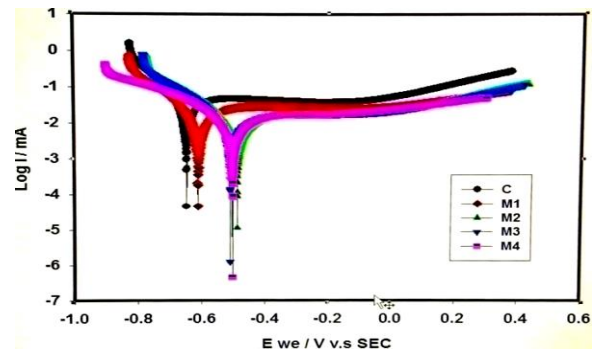


Fig. 13. Potentiodynamic polarization curve of reinforced concrete samples

Moreover, corrosion parameters calculated from Tafel Plots measured for tested samples were listed in Table 11. It is found that, C sample have the highest corrosion current (I_{corr}) and corrosion rate value and thus the lowest Rpvalue. This means that C sample have the lowest corrosion inhibition. While, corrosion rate values decreased gradually from 2.66911×10^{-3} mm/year For C, to 1.14374×10^{-3} , 0.969358×10^{-3} , 0.856192×10^{-3} and 0.41548×10^{-3} for M1, M2, M3 and M4 respectively. These results confirms with the corrosion current density values which decreased gradually from $5.021 \mu A/cm^2$ for C, to 3.909, 2.613, 2.068, 1.420 for M1, M2, M3 and M4, respectively. This indicated that corrosion inhibition enhanced gradually by increasing the content of NS content. This obviously observed from Rp values, which increased from 1215 Ohm for C to 1404, 1628, 2542 and 5378 for M1, M2, M3 and M4 respectively. These results indicated that, corrosion inhibition increased by increasing Ns addition content. This is because of nanosilica addition improves durability and pore structure of concrete (as confirmed by SEM). Where, nano-silica decreased porosity and accordingly permeability decreased causing decrease in the current density and consequently corrosion rate decreased. Moreover, this result is in accord with the higher resistivity of the NS-containing concretes and may be associated to the fine porosity of the Ns-containing concretes [34]. Sharkawi et al. observed that, the optimum ratio for corrosion resistance of reinforced concrete was 2% NS and 8% MS as a replacement ratio [22]. While Elfeky et al. investigated that, 4.5 % Ns is the optimum

Table (11): Corrosion parameters obtained from Tafel Plots for reinforcement concrete samples

Sample notation	O.C.P Results	Electrochemical measurements values obtained from OCV and potentiodynamic anodic polarization technique		RP (Ohm)
	$E_{corr}(V)$	Corrosion current density $I_{corr}(\mu A/cm^2)$	Corrosion rate (mm/year)	
C	-0.646	5.021	2.66911×10^{-3}	1215
M1	-0.4835	3.909	1.14374×10^{-3}	1404
M2	-0.4086	2.613	0.969358×10^{-3}	1628
M3	-0.3935	2.068	0.856192×10^{-3}	2542
M4	-0.2522	1.420	0.41548×10^{-3}	5378

replacement ratio for corrosion resistance of reinforced concrete [35]. Also, Radhakrishnan et al. reported that, the corrosion resistance in concrete improved gradually as the nanosilica content increased [36].

CONCLUSION

1- The physical and mechanical properties of concrete improved gradually with the addition of nano-silica to concrete mix design at specific limits of addition.

2- The highest compressive strength value at 28 days in a mixture with nano-silica 2% i.e 64.2 MPa.

3- The addition of nanosilica more than 2% can result in agglomeration during the mixing and consequently resulting in decreasing the compressive strength. The decrease in the compressive strength can be caused when the distribution mixing of nanosilica were added to the concrete uneven, in part, on the agglomeration and therefore cannot fill the pores in the mortar.

4- Nanosilica improves the microstructure of concrete.

5- The using of nanosilica improves the corrosion inhibition of steel rebar in reinforced concrete.

REFERENCES

- [1] Sakr OM and Alhablain EA. Assessment of the Knowledge and Attitude of Dental Students and Intern Practitioners about the Nanotechnology in Dentistry at KSA", *International Archives of Integrated Medicine* 2018; 5 (10): 87-94.
- [2] Khan MS, *Nanotechnology in Transportation: Evolution of a Revolutionary Technology*. TR News November-December 2011; No 277: pp. 3-8,
- [3] Gavaskar A, Rojas D and Videla F. Nanotechnology: the scope and potential applications in orthopedic surgery. *European Journal of Orthopaedic Surgery & Traumatology* 2018; 28 (7): 1257-1260.
- [4] Grove J, Vanikar S and Crawford G "Nanotechnology: New Tools to Address Old Problems", *Journal of the Transportation Research Board*, No. 2141, pp. 47- 51, March 2010.
- [5] Birgisson B and Roque R. Workshop on Nanomodification of Cementitious Materials. University of Florida Gainesville, August 2006.
- [6] Lotfi M, Zineli M and Raufi A. Characteristics of cement mortar containing nano-silica particles. *Iranian Journal of Chemical Engineering* 2009; 8(44): 23-44.
- [7] Abd El-Aleem S, Heikal M, Morsi WM. Hydration characteristic, thermal expansion and microstructure of cement containing nano-silica. *Construction and Building Materials Journal* 2014; 59 (30): 151-160.
- [8] Prasa da Rao DV, Kumar MP. A study on influence of fly ash and nanosilica on strength properties of concrete. *International Journal of Research in Engineering and Technology* 2014; 5(7): 94-102.
- [9] El-Didamony H, Abd El-Aleem S and Ragab A. Hydration behavior of composite cement containing fly ash and nanosized SiO₂. *American Journal of Nano Research and Applications* 2016; 4(2): 6-16.
- [10] Tawfik T. A., AbdEl-Aziz M. A., Abd El-Aleem S. and Faried A. S. Influence of nano particles on mechanical and nondestructive properties of high-performance concrete. *Journal of Chinese Advanced Materials Society* 2018; 1-25.
- [11] Ozyildirim C. Laboratory Investigation of nanomaterials to improve the permeability and strength of concrete. *Virginia Transportation Research Council- VTRC 10-R182010*; 1-16.
- [12] Mohammed AB. Behavior of binary and ternary blended cement concrete incorporating nano materials. *Engineering Research Journal Faculty of Engineering Helwan University* 2014; 141.
- [13] Isfahani FT, Redaelli E, Lollini F, Li W and Bertolini L. Effects of Nanosilica on Compressive strength and durability properties of concrete with different water to binder ratios. *Advances in Materials Science and Engineering* 2016; 1-16.
- [14] Montgomery J, Abu-Lebdeh T, Hamoush SA and Picornell M. Effect of nano silica on the compressive strength of harden cement paste at different stages of hydration. *American Journal of Engineering and Applied Science* 2016; 9 (1): 166-177.
- [15] Younis KH and Mustafa SM. Feasibility of using nanoparticles of SiO₂ to improve the performance of recycled aggregate concrete. *Advances in Materials Science and Engineering* 2018; 2018:1-11.

- [16] Li W, Huang Z, Cao F, Sun Z and Shah SP. Effects of nano-silica and nano-limestone on flow-ability and mechanical properties of ultra-high-performance concrete matrix. *Construction and Building Materials* 2015; 95: 366-374.
- [17] Shaikh FUA, Supit SWM and Sarker PK. A study on the effect of nano silica on compressive strength of high volume fly ash mortars and concretes. *Materials & Design* 2014; 60: 433-442.
- [18] Shah SP, Hou P and Konsta-Gdoutos MS. Nanomodification of cementitious material: toward a stronger and durable concrete. *Journal of Sustainable Cement-Based Materials* 2016; 5:1-22.
- [19] Ghosh A, Sairam V and Bhattacharjee B. Effect of nano-silica on strength and microstructure of cement silica fume paste, mortar and concrete. *Indian Concrete Journal* 2013; 87(6):11-25.
- [20] Yu R, Spiesz P. and Brouwers HJH. Effect of nano-silica on the hydration and microstructure development of Ultra-High Performance Concrete (UHPC) with a low binder amount. *Construction and Building Materials* 2014; 65: 140-150.
- [21] Eskandari-Naddaf H and Ziaei-Nia A. Simultaneous effect of nano and micro silica on corrosion behaviour of reinforcement in concrete containing cement strength grade of C-525. *Procedia Manufacturing* 2018; 22: 399-405
- [22] Sharkawi AM, Abd-Elaty MA and Khalifa AH. Synergistic influence of micro-nano silica mixture on durability performance of cementitious materials. *Construction and Building Materials* 2018; 164: 579-588.
- [23] Tawfik T. A., El-Yamany M. A., Abd El-Aleem S., Gaber A. S. and AbdEl-Hafez Gh. M. Effect of nanosilica and nanomaterial waste on durability and corrosion rate of steel reinforcement embedded in high-performance concrete. *Asian Journal of Civil Engineering* 2019; 20: 147-135.
- [24] Abdel-Baky S, Yehia S and Khalil IS. Influence of nano-silica addition on properties of fresh and hardened cement mortar. 5th International Conference Nanocon 2013, Czech Republic
- [25] Beigi M H, Berenjian J, Omran OL, Nik AS and Nikbin IM. An experimental survey on combined effects of fibers and nanosilica on the mechanical, rheological, and durability properties of self-compacting concrete. *Materials and Design* 2013; 50:1019-29.
- [26] Lone SS, Gupta M and G Mehta. Comparative Study of Nano-Silica Induced Mortar, Concrete and Self-Compacting Concrete – A Review. *Indian Journal of Science and Technology* 2016; 9(44): 1-7.
- [27] Qing Ye, Zenan Z, Deyu K and Rongshen. Influence of nano-SiO₂ addition on properties of hardened cement paste as compared with silica fume. *Construction and Building Materials* 2007; 21(3): 539-545.
- [28] Bahadori H and Hosseini P. Reduction of cement consumption by the acid of silica nanoparticles (investigation on concrete properties). *Journal of Civil Engineering and management* 2012; 18(3): 416-425.
- [29] Li W, Long C, Tam VWY, Poon CS and Duan WH. Effects of nano-particles on failure process and microstructural properties of recycled aggregate concrete. *Construction and Building Materials* 2017; 142: 42-50.
- [30] Mukharjee BB and Barai SV. Influence of nano-silica on the properties of recycled aggregate concrete. *Construction and Building Materials* 2014; 55: 29-37.
- [31] Li W, Luo Z, Long C, Wu C, Duan W H and Shah SP. Effects of nanoparticles on the dynamic behaviors of recycled aggregate concrete under impact loading. *Materials & Design* 2016; 112: 58-66.
- [32] Esmaeili J and Andalibi K. Investigation of the effects of nano-silica on the properties of concrete in comparison with micro-silica. *International Journal of Nano Dimension* 2012; 3(4): 321-328.
- [33] Setiati NR. Effects of additional nanosilica of compressive strength on mortar. *Innovation in Polymer Science and Technology* 2016; 223: 550-561.
- [34] Dotto JMR, de Abreu AG, Dal Molin DCC and Muller IL. Influence of silica fume addition on concrete's physical properties and on corrosion behavior of reinforcement bars. *Cement & Concrete Composites* 2004; 26: 31-39.
- [35] Elfeky MS, Serag MI, Yasien AM and Elkady H. Bond strength of nanosilica concrete subjected to corrosive environments. *ARP Journal of Engineering and Applied Sciences* 2016; 11(23): 13909-13924.
- [36] Radhakrishnan V and Perumal Pillai EP. Influence of nano silica addition on the behavior of concrete and its impact on corrosion resistance. *Journal of Computational and Theoretical Nanoscience* 2018; 15(2):530-536.

الملخص العربى

يهدف هذا البحث الى رفع كفاءة الخرسانة المسلحة والعادية وذلك عن طريق اضافة مادة النانو سيليكات الى لها تأثير فعال فى تحسين خواص الخرسانة وتثبيت تآكل حديد التسليح. بعد توصيف المواد المستخدمة فى الدراسة تم استخدام النانو سيليكات فى الخلطات الخرسانية وذلك باضافاتها للخلطات بنسب مختلفة؛ النسب تتراوح من 0,5 - 2,5 من وزن الاسمنت. تم دراسة تأثير نسب الاضافة على خواص الخرسانة مثل قابلية التشغيل والكثافة. تم عمل مكعبات خرسانية من الخلطات المحضرة وتم تقييمها من حيث قوة الانضغاط وجد ان مادة النانو سيليكات تساهم بشكل كبير فى رفع قيمة قوة الانضغاط للخرسانة وذلك لانها تتفاعل مع هيدروكسيد الكالسيوم الناتج من عملية الهيدرة أثناء تحضير الخرسانة وتكون مادة الكالسيوم سيليكات هيدريت التى تتواجد فى المناطق البيئية بين الركام والعجينة الاسمنتية مما يتسبب فى غلق مسامات الخرسانة المتصلدة ورفع كفاءتها ؛ وتم تأكيد ذلك من خلال الفحص المجهرى للمناطق البيئية وذلك عن طريق الميكروسكوب الالكترونى . وجد أن اضافة النانو سيليكات تساهم بشكل كبير فى تحسين الخرسانة وذلك حتى نسبة اضافة 2% من وزن الاسمنت ولكن لوحظ أنه عندما تزداد الاضافة عن هذه النسبة فان كفاءة الخرسانة تنخفض. وأخيرا تم دراسة تأثير اضافة النانو سيليكات على تثبيت تآكل حديد التسليح فى الخرسانة المسلحة وتوصلنا الى أن النانو سيليكات لها دور فعال فى تثبيت تآكل حديد التسليح الناتج عن تعرض المنشآت الخرسانية للبيئات الضارة المختلفة والتى تؤدي الى انهيار الأبنية الخرسانية.